Modeling on Emulsification of Slag and Metal in Shaking Ladle

S. Q. Ni [1], S. J. Chu [1], J. Zhang [2]

[1] School of Metallurgical and Ecological Engineering, University of Science and Technology Beijing, Beijing, 100083, China; nishanqiang@126.com, chushaojun@metall.ustb.edu.cn
[2] School of Metallurgy and Resource, Anhui University of Technology, Ma'anshan, 243002, China; zhjxsj@126.com.

Abstract

The shaking ladle is one of the main equipment for producing low & medium carbon ferromanganese with electric furnace-shaking ladle process. The emulsification behaviour of slag and metal in shaking ladle has been studied experimentally using low-temperature oil and water. The entrainment critical shaking speed (ECSS) was defined as the lowest shaking speed at which the entrainment of slag occurs. It was found that the ECSS was decreased with the increasing of ladle diameter, eccentric distance and the density of the lower phase, and was increased with the increasing of lower phase height, the height difference and the density difference of the two phases, the viscosity of the two phases. An empirical equation for the ECSS was proposed as a function of ladle diameter, eccentric distance, the height and physical properties of the liquids.

KEYWORDS: *shaking ladle; emulsification; entrainment critical shaking speed.*

1. Introduction

Low-carbon ferromanganese (LC FeMn) alloys are preferred for the production of low-carbon steel and other special grades of steel. Two principal methods of producing LC FeMn are in commercial operation. The first one is silicothermal reduction and the second is manganese oxygen refining process (MOR)[1]. Because of the high SiO_2 content of Chinese manganese ores, the siliconthermal reduction method is widely used in China [2]. The refining furnace-shaking ladle process is the most popular one for producing LC FeMn nowadays. A flow-chart of the process is shown in Fig. 1.
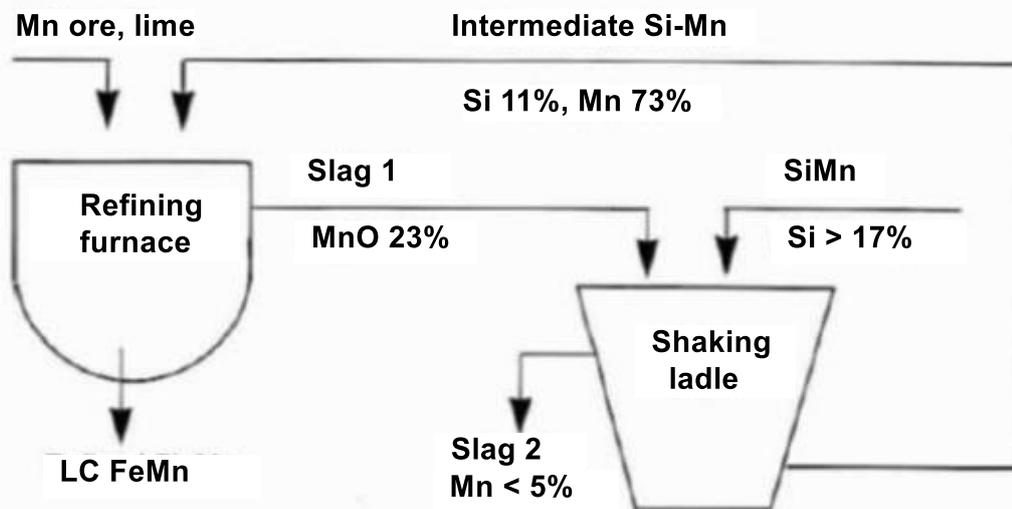

Fig. 1. Flow chart for the refining furnace-shaking ladle process for the production of LC FeMn[2]

The shaking ladle was developed by Kalling[3] at Domnarvet, Sweden in 1958. The shaking ladle has been proved as an excellent metallurgical tool wherever it is necessary to obtain good mixing, for instance, in desulfurization, recarburization and alloying of pig iron[4], production of low and medium carbon ferromanganese and ferrochrome[5], processing of ferrovanadium[6] and stainless steel[7].

The single-phase liquid mixing phenomena in shaking ladle has been investigated by different researchers [3,8-9]. Eketorp [3] measured the wave heights in the bath during shaking in different speeds, and proposed the definition of critical shaking speed, nc, at which a characteristic wave motion was created which looks like a breaker and the wave height in the bath reached a maximum value. Ishii[8]and Tsai [9] continued studies in this field and proposed their empiri-

The Fourteenth International Ferroalloys Congress
Energy efficiency and environmental friendliness are the future of the global Ferroalloy industry

May 31-June 4, 2015
Kiev, Ukraine

636

cal equations for the nc as a function of R (radius of ladle, mm), H (height of bath, mm) and a (eccentricity, mm). In the earlier paper[10], the present authors proposed another way to investigate the mixing efficiency in shaking ladle bath by measuring the mixing time, and a new critical shaking speed was defined based on mixing time. In addition, a bioreactor named orbitally shaken bioreactor which is used for the cultivation of mammalian cells has drawn the attention in recent years, and a lot of research results were reported about the single phase liquid behaviour[11-16].

However, the mixing phenomena of two immiscible liquids have not been reported yet, though it is very important for the LC carbon FeMn. In the present work, the mixing process of slag/metal in shaking ladle was studied using low-temperature oil/water analogues. And an empirical equation for the slag entrainment critical shaking speed was proposed.

2. Experimental Apparatus and Procedure

Figure 2 shows a schematic of the experimental apparatus. Water and one of the two oils listed in Tab. 1 were contained in a cylindrical vessel made of transparent acrylic resin. Three vessels were used, with different size (D=0.19 m, 0.24 m, 0.29 m). The vessel was placed on the shaking frame. The eccentricity can be continuously set within the range of 0~50 mm. The liquids behaviours were recorded by a high speed camera with a capture rate of 200 fps.
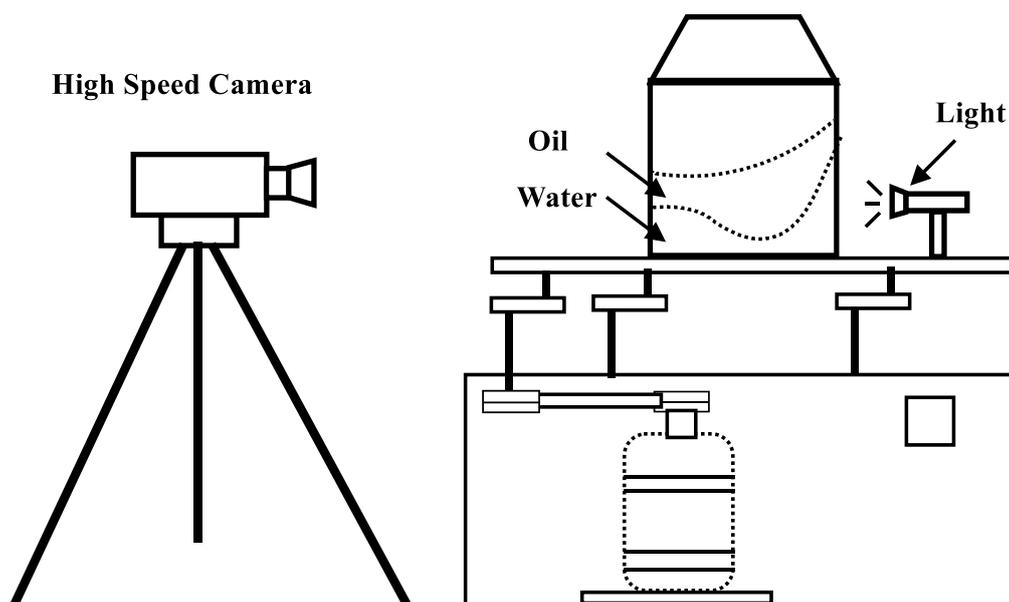

Fig. 2. Experimental apparatus

Tab 1: Operating variables and their ranges of model experiments

Liquid	Density (kg/m^3)	Viscosity (mPa·s)	Surface tension (mN/m)	Interface tension with water (mN/m)
Bean oil	926	71.8	31.2	13.4
Machine oil	933	103.2	32.0	12.0

3. Experimental Phenomena

As described in an earlier paper [17] of the present authors, with the increase in the shaking speed the flow patterns of two liquid phases in shaking ladle could be classified into three types: interface oscillatory pattern, lotus-leaf-like pattern and entrainment pattern (Fig 3). The two layers will maintain stratified status when the shaking speed is low, just as the interface oscillatory pattern and lotus-like pattern shows. However, the lower liquid will be entrained into the upper liquid with the increase in the shaking speed, and the entrainment pattern formed. The lowest shaking speed at which the entrainment of slag occurs is defined as the entrainment critical shaking speed (ECSS).
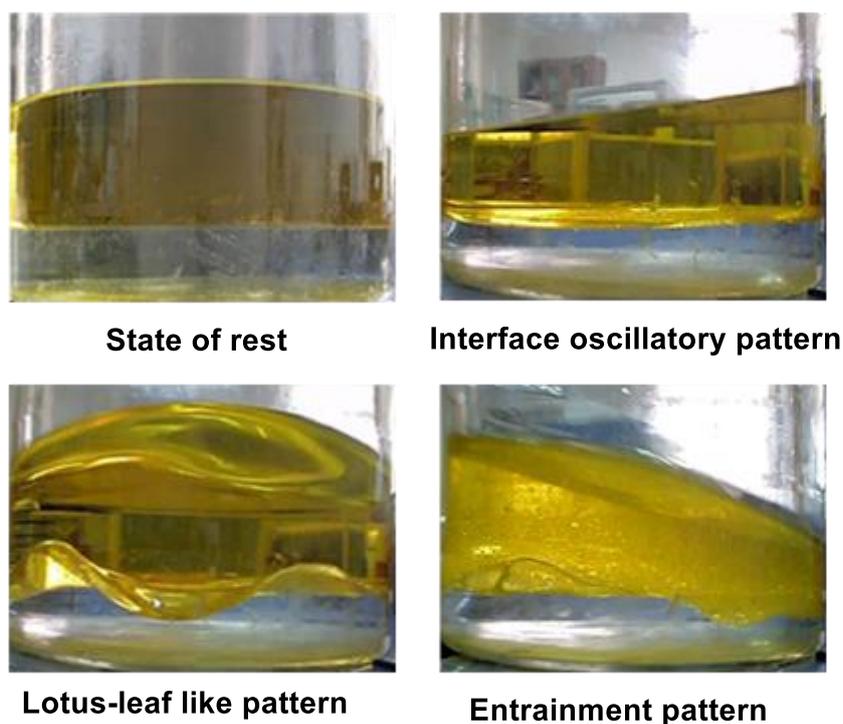
The Fourteenth International Ferroalloys Congress
**Energy efficiency and environmental friendliness
are the future of the global Ferroalloy industry**

May 31-June 4, 2015
Kiev, Ukraine

637

State of rest   **Interface oscillatory pattern**

Lotus-leaf like pattern   **Entrainment pattern**

Fig. 3. The flow patterns under different shaking speeds

4. Results and Discussions

4.1 Effect of ladle diameter on ECSS

The effect of ladle diameter on ECSS was studied with 3 different ladles, and the oil used in this experiment was bean oil. The experimental conditions are shown in Table 2. The relationships between ECSS and ladle diameter at four eccentric distances are shown in Fig. 4.

Tab. 2. Experimental conditions

Ladle diameter/m	Oil height/10^{-2}m	Water height/10^{-2}m
0.19	4.4	2.9
0.24	5.5	3.7
0.29	6.7	4.5

The Fourteenth International Ferroalloys Congress
**Energy efficiency and environmental friendliness
are the future of the global Ferroalloy industry**
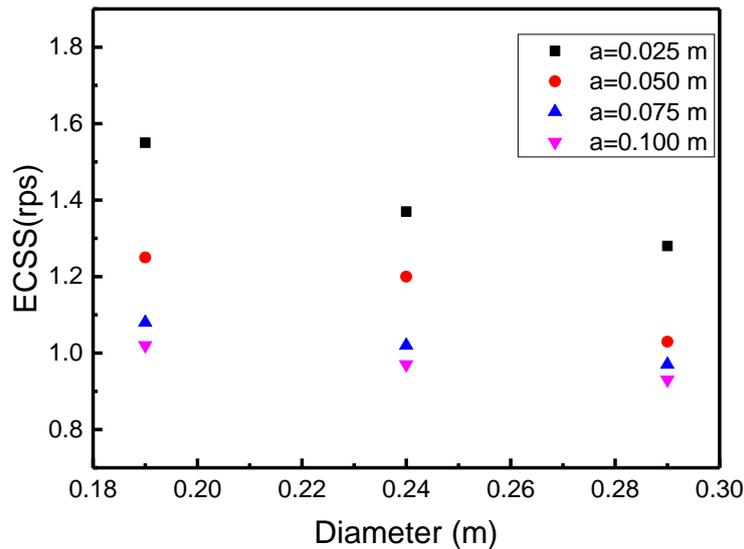
May 31-June 4, 2015
Kiev, Ukraine

638

Fig. 4. Effect of shaking ladle diameter on ECSS

As can be seen from Fig. 4, the ECSS decreases with the increase in ladle diameter. It indicates that bigger ladle is more favourable for the mixing of slag and metal in shaking ladle. In addition, the dissipating heat of unit volume molten liquid in a bigger vessel is less than that in a smaller one, which will reduce the heat loss in the process of production.

4.2 Effect of liquid height on the ECSS

The ladle diameter used in this experiment is 0.29 m and the eccentric distance is 1.5 cm. The height of water is 3.4 cm, and the height ratio of oil and water varies with the change of bean oil height. The effect of liquid height ratio on the ECSS is shown in Fig. 5. It can be seen from Fig. 5 that the ECSS increased with the increasing height ratio of the two phases. It indicates that the less slag was better for mixing of slag and metal. When the amount of slag increases, the shaking speed should be increased in order to promote better two-phase mixing.
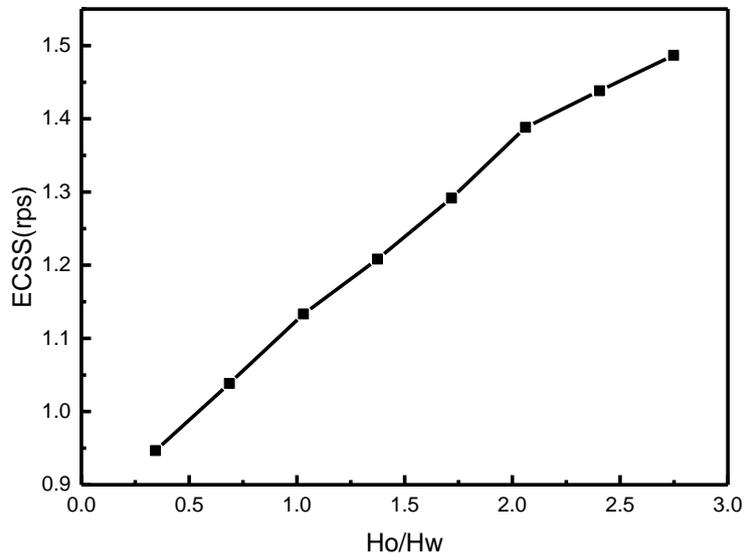

Fig. 5. Effect of height ratio of oil and water volume on ECSS

4.3 Effect of eccentric distance on the ECSS

The value of eccentric distance determines the shaking amplitude of the shaking ladle, which is very important for the emulsification of slag and metal. The effect of eccentric distance on the ECSS was investigated in three ladles with different diameters. The experimental results are shown in Fig. 6. As can be seen from Fig. 6, the ECSS decreases with the increase in the eccentric distance indicating that a larger eccentric distance is favourable for the emulsification of the
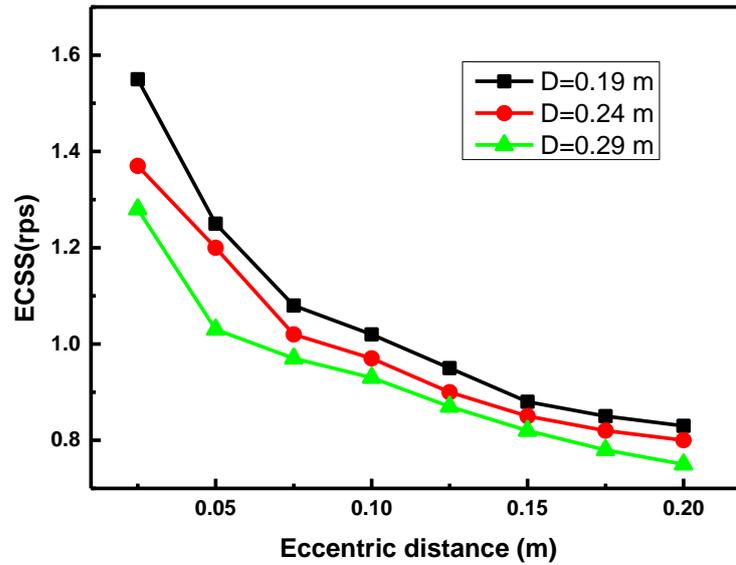
The Fourteenth International Ferroalloys Congress
**Energy efficiency and environmental friendliness
are the future of the global Ferroalloy industry**

May 31-June 4, 2015
Kiev, Ukraine

639

two phases.

Fig. 6. Effect of eccentric distance on ECSS

4.4 Effect of upper phase property on the ECSS

In actual production, slag phase composition and physical parameters will be different depending on different products. Bean oil and machine oil were used to investigate the effect of upper phase property of ECSS in shaking ladle. The properties of the two oils are listed in Table 1. It can be seen from Table 1 that the main difference between the two oils is the value of viscosity. The experimental result is shown in Fig. 7. As can be seen from Fig. 7, the ECSS for machine oil-water system is lower than that for the bean oil-water system. It indicates that the lower viscosity makes mixing easier.
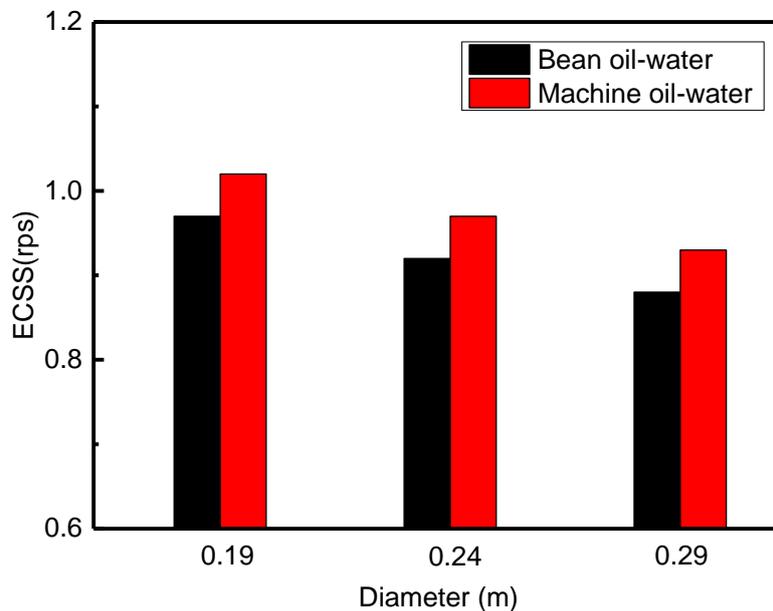

Fig. 7. Effect of upper phase property on ECSS

4.5 Effect of lower phase density on the ECSS

Gravity is the main force to stabilize the interface of two phases in shaking ladle. A NaCl aqueous solution was used to investigate the effect of lower phase density on ECSS. The densities of the three liquids are listed in Table 3. The experimental results are shown in Fig. 8. It can be seen that the bean oil-NcCl aqueous solution system, for which the density difference is bigger, is easier to mix with each other in shaking ladle when the height ratio of the two-phase

The Fourteenth International Ferroalloys Congress
**Energy efficiency and environmental friendliness
are the future of the global Ferroalloy industry**

May 31-June 4, 2015
Kiev, Ukraine

640

is small. However, with the increase in the ratio, the effect of the lower phase density decreased and could be ignored.

Tab. 3. The density differences between the two systems

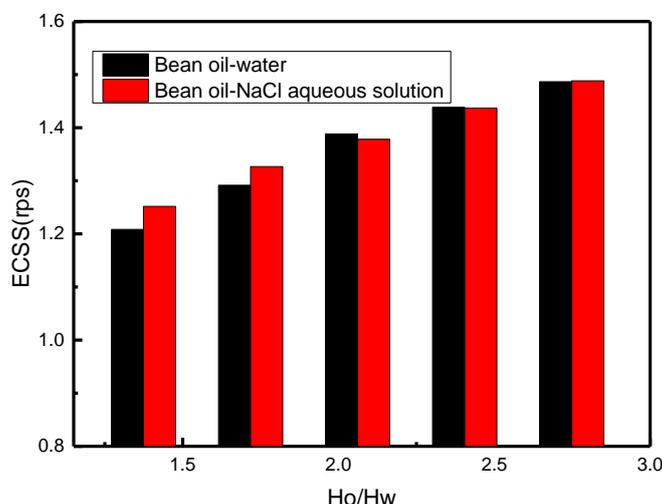|	**Bean oil-water**	**Bean oil-NaClaqueous solution**
Lower phase density （kg/m^3）	1000	1190
Upper phase density （kg/m^3）	926	926
Density difference （kg/m^3）	74	264

Fig. 8. Effect of lower phase density on ECSS

4.6 Dimensional analysis

Based on experimental results and the preceding discussion, one can carry out a preliminary dimensional analysis by assuming that the ECSS is dependent on the variables listed in the following correlation:

$$N_{ce} = f(D, a, H_w, \Delta H, \mu_o, \mu_w, \rho_w, \Delta\rho, \sigma_{ow}, g) \tag{1}$$

where N_{ce} (rps) is the ECSS; D (m) is the ladle diameter; a is the eccentric distance; H_w (m) is the lower phase height; ΔH (m) is the height difference of lower and upper phases; μ_w(Pa·s) is the viscosity of water andμ_o(Pa·s) is the viscosity of oil; ρ_w (kg/m^3) is the density of lower phase and $\Delta\rho$ (kg/m^3) is the density difference of lower and upper phases; σ_{ow} is the interfacial tension between the two liquids; g is the gravitational constant.

In Eq. (1), there are 11 variables and three fundamental dimensions; therefore, eight dimensionless groups are to be obtained:

$$\pi_1 = \frac{D}{H_w} \tag{2}$$

$$\pi_2 = \frac{a}{H_w} \tag{3}$$

$$\pi_3 = \frac{\Delta H}{H_w} \tag{4}$$

$$\pi_4 = \frac{\rho_w^2 g H_w^3}{\mu_o^2} \tag{5}$$

$$\pi_5 = \frac{\rho_w^2 g H_w^3}{\mu_w^2} \tag{6}$$

$$\pi_6 = \frac{\Delta\rho}{\rho_w} \tag{7}$$

$$\pi_7 = \frac{\rho_w g H_w^2}{\sigma_{ow}} \tag{8}$$

The Fourteenth International Ferroalloys Congress　　　　　　　　　　　　　　　May 31-June 4, 2015
Energy efficiency and environmental friendliness　　　　　　　　　　　　　　　Kiev, Ukraine
are the future of the global Ferroalloy industry

641

$$\pi_8 = \frac{N_c^2}{gH_w} \qquad (9)$$

Through dimensional analysis, the Eqs. (2) to (9) lead to the functional relationship that

$$\pi_8 = f(\pi_1, \pi_2, \pi_3, \pi_4, \pi_5, \pi_6, \pi_7) \qquad (10)$$

or, for the first memeber of a polynomial series, that

$$\pi_8 = K\pi_1^{\alpha_1} \pi_2^{\alpha_2} \pi_3^{\alpha_3} \pi_4^{\alpha_4} \pi_5^{\alpha_5} \pi_6^{\alpha_6} \pi_7^{\alpha_7} \qquad (11)$$

By applying multiple regression analysis to the experimental results, the following relationship between the ECSS and other independent variables was obtained:

$$N_{ce} = 2.36 \times 10^4 D^{-0.83} a^{-0.27} H_w^{0.51} \Delta H^{0.07} \mu_o^{0.05} \mu_w^{0.74} \rho_w^{-0.80} \Delta\rho^{0.12} \qquad (12)$$

Fig. 9 compares the measured values and calculated values of the ECSS at different experimental conditions. The measurement is approximated by Eq. (12) with a scatter of ±10%.
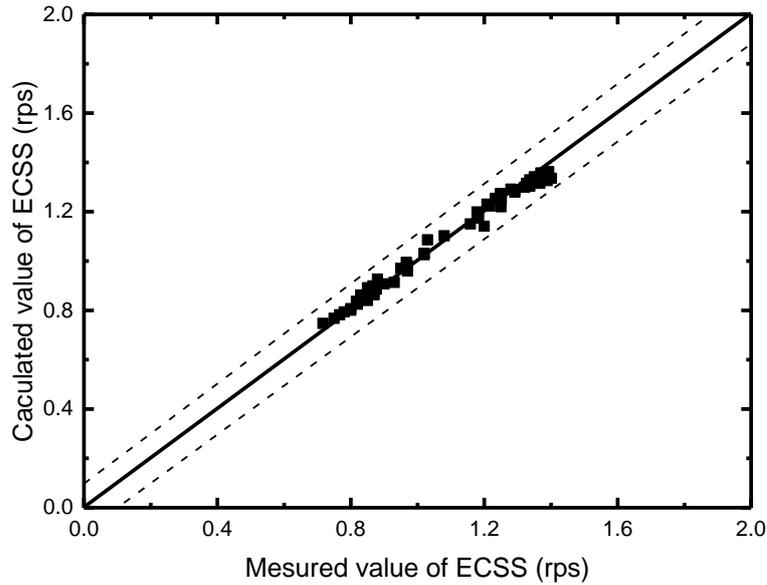

Fig. 9. Relation between measured and calculated values of ECSS

5. Conclusion

The entrainment critical shaking speed has been studied experimentally using bean oil-water system and machine oil-water system. From the present work, the following conclusions can be drawn:

(1) The ECSS was decreased with the increase in the ladle diameter, eccentric distance and the density of the lower phase, and was increased with the increase in lower phase height, the height difference and the density difference of the two phases, the viscosity of the two phases;

(2) Dimensional analysis was used to express the empirical equation of ECSS. With the present modelling study, the empirical equation can be expressed as follows: $N_{ce} = 2.36 \times 10^4 D^{-0.83} a^{-0.27} H_w^{0.51} \Delta H^{0.07} \mu_o^{0.05} \mu_w^{0.74} \rho_w^{-0.80} \Delta\rho^{0.12}$.

Acknowledgements

[1] M. Gasik. Handbook of ferroalloys: theory and technology. Oxford: Butterworth-Heinemann, 2013.
[2] J. H.Zhou, Z. Z.Yang. The development of technology for the production of refined ferromanganese in China [C]. INFACON 6. Proceedings of the international ferroalloys congress, Cape Town. Volume 1. Johannesburg, SAIMM, 1992: 145-147.
[3] S. Eketorp. The mixing ladle, a new metallurgical tool [J]. Journal of Metals, 1960, (1): 44-48.
[4] G. J. Jenkins. The application of the shaking ladle for treatment of molten metal at BSC Landore foudry[J]. British Foundryman, 1979, Jun, Suppl. 151-153.

The Fourteenth International Ferroalloys Congress
**Energy efficiency and environmental friendliness
are the future of the global Ferroalloy industry**
May 31-June 4, 2015
Kiev, Ukraine

642

[5]   O. Shinichi: Production of medium carbon ferro-manganese by the shaking ladle. INFACON 3 Conference Proceedings, Tokyo, Japan 1983, pp. 194-199.

[6]   B. Rohrmann: Vanadium in South Africa. Journal of the South Africa Institute of Mining and Metallurgy. 85(1985), (5), 141-150.

[7]   P. Chen, S. Chu, H. Wang, A new process to produce 300 series stainless steel with electric-silicothermic method[C], Proceedings of the thirteen international ferroalloys congress, Almaty, 2013, pp. 791-798.

[8]   K. Ishii: Metallurgical uses of the shaking converter (III)—motion of the bath. Suiyo Kaishi, 15(1964), (5), 253-258.

[9]   C. P. Tsai, Z. M. Qian: Model study on shaking ladle. Transactions ISIJ, 26 (1986): 139.

[10]   S. Q. Ni, H. J. Wang, J. Zhang, S. J. Chu. Effects of bath depth and eccentricity on mixing phenomena in shaking ladle [J]. High temperature materials and processes. (DOI:10.1515/htmp-2014-0013)

[11]   Büchs J. Introduction to advantages and problems of shaken cultures [J]. Biochemical Engineering Journal, 2001, 7: 91-98.

[12]   Weheliye W, Yianneskis M, Ducci A. On the fluid dynamics of shaken bioreactor-flow characterization and transition [J]. AIChE Journal, 2013, 59(1): 334-344.

[13]   Tissot S. OrbShake bioreactors for mammalian cell cultures: engineering and scale-up [D]. Advisor: Wurm F. Lausanne: Ecole Polytechnique Federale de Lausanne, 2011.

[14]   Micheletti M, Barrett T, Doig S D, et al. Fluid mixing in shaken bioreactors: implications for scale-up predictions from microliter-scale microbial and mammalian cell cultures [J]. Chemical Engineering Science, 2006, 61: 2939-2949.

[15]   Zhang X W, Burki C A, Stettler M et al. Efficient oxygen transfer by surface aeration in shaken cylindrical containers for mammalian cell cultivation at volumetric scales up to 1000 L [J].Biochemical engineering journal, 2009(45): 41-47.

[16]   Rodriguez G, Anderlei T, Micheletti M, et al. On the measurement and scaling of mixing in orbitally shaken bioreactors [J]. Biochemical Engineering Journal, 2014,82: 10-21.

[17]   J. Zhang, S. J. Chu, S. Q. Ni. Simulation experiments on two-phase flows in shaking ladle[J]. Advanced Materials Research, 2011, v 228-229, 390-395.

The Fourteenth International Ferroalloys Congress   May 31-June 4, 2015
Energy efficiency and environmental friendliness   Kiev, Ukraine
are the future of the global Ferroalloy industry

643